

utilization of Breed Chicken Eggshells for Biodisel

by Agus Purnomo

Submission date: 12-May-2023 08:16AM (UTC+0700)

Submission ID: 2090885248

File name: Jurnal_utilization_of_Breed_Chicken_Eggshells_for_Biodisel.pdf (534.1K)

Word count: 2947

Character count: 16056



Utilization of Breed Chicken Eggshells for Biodiesel Preparation from Waste Cooking Oil

Rodhiansyah Djayasinga*, Andi Setiawan, Agus Purnomo, Ahmad Zakaria Amien, and Hertanti Hertanti

Received : April 30, 2021

Revised : October 28, 2021

Accepted : October 30, 2021

Online : November 01, 2021

Abstract

Chicken eggshell waste is a promising source of CaO which can be converted into heterogeneous catalyst materials. The purpose of this study was to utilize CaO heterogeneous catalyst derived from breed chicken eggshell to produce biodiesel from waste cooking oil through the transesterification process. A total of 4 g of catalyst material was mixed with 200 g of waste cooking oil and 60 g of methanol, and then the mixture was stirred at a speed of 700rpm for 6 h at $60 \pm 4^\circ\text{C}$. The produced biodiesel was analyzed using GC-MS to elucidate the various methyl ester compounds. The produced biodiesel was found to have a density of 855kg/m^3 , viscosity of $3.74\text{ mm}^2/\text{s}$ (cSt), and flash point of 135°C . Based on these results, it can be concluded that breed chicken eggshells are potential sources for the preparation of CaO catalyst material to produce biodiesel from waste cooking oil. This finding is very useful for further optimization of mass catalysts heterogeneous CaO from breed chicken eggshells including the commercial production of biodiesel.

Keywords: biodiesel, CaO heterogeneous catalyst, transesterification, waste cooking oil, breed chicken eggshell

1. INTRODUCTION

Recently, it is well known that breed chicken eggshells are simply discarded polluting our environment. Whereas the breed chicken eggshells waste is a calcium resource that can be utilized as a raw material for the production of CaO heterogeneous catalyst [1]–[3]. Based on the composition of existing minerals, the eggshell is composed of CaCO_3 (98.43%), MgCO_3 (0.84%), and $\text{Ca}_3(\text{PO}_4)_2$ (0.75%) minerals. The CaCO_3 itself can be converted into CaO through the calcination process [4].

Catalyst materials are chemicals that can accelerate reactions. The production of a desired chemical compound can be performed using either homogeneous or heterogeneous catalyst. However, the main disadvantage of homogeneous catalysts is their difficulty to be recovered from the reaction system thus resulting in hazardous waste disposal, which is unfavourable [5]. In addition, homogeneous catalysts in free fatty acid (FFA)

transesterification reactions can form soap making it difficult to separate glycerol thus reducing biodiesel yield. Homogeneous catalysts can be replaced with heterogeneous catalysts that are more environmentally friendly, highly stable at high temperatures, large pores, and low-cost material [6]–[9].

Among the other heterogeneous catalysts, CaO has high wetness thus CaO is widely used as a catalyst in the process of transesterification of oil into biodiesel. Another advantage of CaO is its rigid structure so that it is easily recovered at the end of the biodiesel process [10]. The main drawback of CaO catalyst is that it reacts easily with water-containing air to form $\text{Ca}(\text{OH})_2$ leading to a decrement in its catalytic activity [11].

Waste cooking oil (WCO) is a waste generated from vegetable cooking oil that has been used more than three times so that it contains high levels of free fatty acids and peroxides. When WCO is still consumed by humans it can cause serious diseases including high blood pressure and cancer. Food processing using cooking oils leaves WCO and often it is discharged through public sewers, resulting in environmental pollution such as foam formation and sludge flotation. This problem is slowly but sure affects human life and requires expensive environmental remediation costs [12]–[15].

Researchers have reported the utilization of CaO catalysts to convert WCO into biodiesel products. Zhang et al. synthesize Au/CaO nanoribbons that can be used as recyclable catalysts with high activity for biodiesel production [16]. Yan et al.

Copyright Holder:

© Djayasinga, R., Setiawan, A., Purnomo, A., Amien, A.Z. and Hertanti, H. (2022)

First Publication Right:

Journal of Multidisciplinary Applied Natural Science

Publisher's Note:

Pandawa Institute stays neutral with regard to jurisdictional claims in published maps and institutional affiliations.

This Article is Licensed Under:





Figure 1. The synthesis scheme of CaO heterogeneous catalysts from pure breed chicken eggshells.

used WCC with a dose of 6% to convert cooking oil waste in 82% biodiesel yield [17]. Alptekin et al. conducted a reduction of FFA content using acid catalysts and then produced biodiesel using alkaline catalysts [18]. Dang et al. convert WCO from canteen source to biodiesel [19]. Xiong et al. convert alcohol made from used cooking oil waste into biodiesel [20]. Marchetti conducted a study on the comparison of biodiesel products produced using raw materials for new cooking oil and used cooking oil, the results obtained were 40% of biodiesel products [21]. Agarwal et al. produced biodiesel by converting used cooking oil into biodiesel using a KOH catalyst in 98.2% yield [22]. Considering some of the aspects described above, the study aims to produce biodiesel from used cooking oil waste taking into account the advantages offered by the heterogeneous catalyst CaO made from pure breed chicken eggshells.

36

2. MATERIALS AND METHODS

2.1. Materials

Used cooking oil and breed chicken eggshell samples were collected from the restaurant in Bandar Lampung City, Lampung, Indonesia. The other chemicals used include: methanol, *n*-hexane, cerium sulfate, and H₂SO₄ purchased from Merck SG.

2.2. Methods

2.2.1. Synthesize CaO heterogeneous catalysts

Pure breed chicken eggshells were washed several times and then boiled. The membrane layer was separated from the shell and then dried at room temperature. Furthermore, the eggshell was crushed into small particles and then filtered. After being crushed, then the material was calcined and sintered using a muffle furnace at 900 °C for 10 h to form a CaO structure [23]. The synthesis scheme of the CaO heterogeneous catalyst is shown in Figure 1.

2.2.2. Preparation of Biodiesel

As much as 200 g of used cooking oil was weighed, added with 60 g of methanol and 4 g of CaO catalyst, and then stirred at $60 \pm 4^\circ\text{C}$ for 6 h. After that, the mixture was allowed to stand for 24 h until 3 phases are formed, namely biodiesel (top layer), glycerol (middle layer), and the catalyst material (bottom part). Crude Biodiesel and glycerol along with the catalyst are separated and placed in another container.

A certain amount of water was then added into the biodiesel mixture for a purification purpose. The crude biodiesel was washed repeatedly until the aqueous phase no longer contained soap and appeared as a clear solution. Finally, the biodiesel was heated at 60 °C for 10 min to evaporate the water which may still be left.



37

Figure 2. Preparation scheme of biodiesel made from waste cooking oil using CaO heterogeneous catalyst.



Figure 3. Rf values of methyl ester produced.

3. RESULTS AND DISCUSSIONS

Based on the screening test using TLC, the obtained Rf values were 0.66 and 0.88 as shown in Figure 3. These results indicate that there were various types of methyl ester compounds with varying carbon chain lengths according to the degree of polarity where the value of 0.88 is relatively more non-polar and has a longer carbon chain than the compounds with an Rf value of 0.66.

Furthermore, the results of the characterization using GC-MS analysis obtained chromatogram data. A total of 18 peaks were observed in the chromatogram, and the first 2 peaks could not be identified because the intensity was too low to be considered satisfactory.

The chromatogram of identified compounds showed in Figure 4 and the composition was presented in Table 1. From Figure 4 and Table 1, the identification of methyl esters indicates that the

transesterification of fatty acids in WCO took place already. The data also showed that methyl octadecanoate was found as the most prominent component of the sample, which was corresponded to the presence of palmitic acid as the most abundant component in WCO [24].

The information presented in Table 2 was an additional analysis to determine the three basic characteristics of biodiesel. Biodiesel standard values according to the Indonesian standard (SNI 7182-2015) are included in Table 2 for comparison. Compared to standard values, all three characteristics are acceptable. In the future, the determination of other parameters included in the standard is required for further commercialization of the produced biodiesel in this study [25]–[27].

4. CONCLUSIONS

The CaO-based heterogeneous catalyst derived from chicken eggshells can be used as a heterogeneous catalyst to produce biodiesel fuel from waste cooking oil as biodiesel raw material. The results of the TLC screening test and GC-MS analysis showed the formation of several methyl ester compounds.

AUTHOR INFORMATION

Corresponding Author

Rodhiansyah Djayasinga — Medical

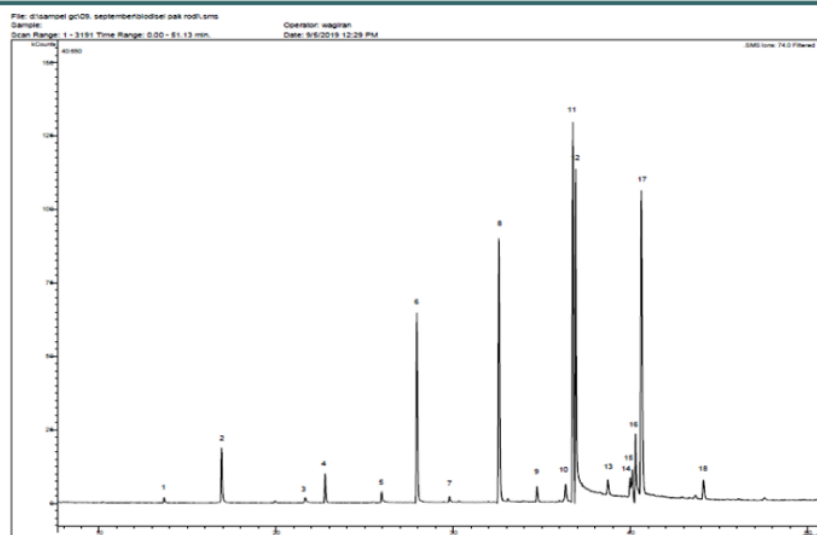


Figure 4. Chromatogram of typical biodiesel produced.

Table 1. The composition of biodiesel produced in this study based on GC-MS analysis.

Peak number	Retention time (min)	MW	m/z	Compound Name	Relative percentage
1	13.670			No hits	0.250
2	16.912			No hits	2.910
3	21.634	444	73	Dodecamethyl-ester	0.320
4	22.757	186	74	Decanoic acid, methyl ester	1.440
5	25.947	518	73	Tetradecamethyl-ester	0.570
6	27.934	214	74	Undecanoic acid, 10-methyl-, methyl ester	9.890
7	29.757	592	355	Hexadecamethyl-ester	0.310
8	32.564	242	74	Tridecanoic acid, 12-methyl-, methyl ester	16.06
9	34.717	256	74	Pentadecanoic acid, methyl ester	0.870
10	36.323	268	74	9-Hexadecenoic acid, methyl ester, (Z)-	1.240
11	36.741	270	74	Pentadecanoic acid, 14-methyl-, methyl ester	21.04
12	36.901	270	74	Pentadecanoic acid, 14-methyl-, methyl ester	16.00
13	38.715	284	74	Hexadecanoic acid, 14-methyl-, methyl ester	0.890
14	39.967	294	67	9,12-Octadecadienoic acid (Z,Z)-, methyl ester	1.110
15	40.099	294	67	8,11-Octadecadienoic acid, methyl ester	1.320
16	40.277	296	264	9-Octadecenoic acid, methyl ester, E-	4.200
17	40.589	298	74	Octadecanoic acid, methyl ester	20.10
18	44.108	326	74	Eicosanoic acid, methyl ester	1.470
Total					100.0

Table 2. Comparison of produced biodiesel with Indonesian Standard for biodiesel.

Parameter Analysis	Result	Standard Value (SNI)
Density at 40 ⁰ C	855 kg/m ³	850-890 kg/m ³ (ASTM D-1298)
Kinematic viscosity at 40 ⁰ C	3.74 mm ² /s (cSt)	2.3-6.0 mm ² /s (cSt) (ASTM D 445)
Flash point (bowl closed)	135 ⁰ C	> 100 ⁰ C (ASTM D 93)

Laboratory Technology, Health Polytechnics
Tanjungkarang, Bandar Lampung - 405308
(Indonesia);

orcid.org/0000000320890795

Email: rodhiansyah@poltekkes-tjk.ac.id

Authors

Andi Setiawan — Department of Chemistry,

University of Lampung, Bandar Lampung -
35145 (Indonesia);

orcid.org/0000-0002-0731-6417

Agus Purnomo — Medical Laboratory
Technology, Health Polytechnics Tanjungkarang,
Bandar Lampung - 405308 (Indonesia);

Ahmad Zakaria Amien — Medical Laboratory
Technology, Health Polytechnics Tanjungkarang,

Bandar Lampung - 405308 (Indonesia);
Hertanti Hertanti — Medical Laboratory
 Technology, Health Polytechnics Tanjungkarang,
 Bandar Lampung - 405308 (Indonesia);

ACKNOWLEDGEMENT

The author would like to thank the Ministry of Health of the Republic of Indonesia for the research funds provided through the Decree of the Director of the Tanjungkarang Health Polytechnics Number. HK.02.03/1.2/2712/2019

REFERENCES

- [1] F. Nadeem, I. A. Bhatti, A. Ashar, M. Yousaf, M. Iqbal, M. Mohsin, J. Nisar, N. Tamam, and N. Alwadai. (2021). "Eco-benign biodiesel production from waste cooking oil using eggshell derived MM-CaO catalyst and condition optimization using RSM approach". *Arabian Journal of Chemistry*. **14** (8): 103263. [10.1016/j.abjc.2021.103263](https://doi.org/10.1016/j.abjc.2021.103263).
- [2] J. Liu, M. Liu, S. Chen, B. Wang, Chen, D. -P. Yang, S. Zhang, and W. Du. (2020). "Conversion of Au(III)-polluted waste eggshell into functional CaO/Au nanocatalyst for biodiesel production". *Green Energy & Environment*. [10.1016/j.gee.2020.07.019](https://doi.org/10.1016/j.gee.2020.07.019).
- [3] P. Maneechakr and S. Kamjanakom. (2021). "Systematic production of biodiesel fuel from palm oil over porous K₂O@CaO catalyst derived from waste chicken eggshell via RSM/kinetic/thermodynamic studies". *Journal of Environmental Chemical Engineering*. **9** (6): 106542. [10.1016/j.jece.2021.106542](https://doi.org/10.1016/j.jece.2021.106542).
- [4] M. Khatibi, F. Khorasheh, and A. Larimi. (2021). "Biodiesel production via transesterification of canola oil in the presence of Na-K doped CaO derived from calcined eggshell". *Renewable Energy*. **163** : 1626–1636. [10.1016/j.renene.2020.10.039](https://doi.org/10.1016/j.renene.2020.10.039).
- [5] F. Yaşar. (2019). "Biodiesel production via waste eggshell as a low-cost heterogeneous catalyst: Its effects on some critical fuel properties and comparison with CaO". *Fuel*. **255** :115828. [10.1016/j.fuel.2019.115828](https://doi.org/10.1016/j.fuel.2019.115828).
- [6] K. D. Pandiangan and W. Simanjuntak. (2013). "Transesterification of coconut oil using dimethyl carbonate and TiO₂/SiO₂ heterogeneous catalyst". *Indonesian Journal of Chemistry*. **13** (1): 47–52. [10.22146/ijc.21325](https://doi.org/10.22146/ijc.21325).
- [7] A. Bavykina, N. Kolobov, I. S. Khan, J. A. Bau, A. Ramirez, and J. Gascon. (2020). "Metal–Organic Frameworks in Heterogeneous Catalysis: Recent Progress, New Trends, and Future Perspectives". *Chemical Reviews*. **120** (16): 8468–8535. [10.1021/acs.chemrev.9b00685](https://doi.org/10.1021/acs.chemrev.9b00685).
- [8] J. Zhong, X. Yang, Z. Wu, B. Liang, Y. Huang, and T. Zhang. (2020). "State of the art and perspectives in heterogeneous catalysis of CO₂ hydrogenation to methanol". *Chemical Society Reviews*. **49** (4): 1385–1413. [10.1039/C9CS00614A](https://doi.org/10.1039/C9CS00614A).
- [9] C. Xie, D. Yan, H. Li, S. Du, W. Chen, Y. Wang, Y. Zou, R. Chen, S. Wang. (2020). "Defect Chemistry in Heterogeneous Catalysis: Recognition, Understanding, and Utilization". *ACS Catalysis*. **10** (19): 11082–11093. [10.1021/acscatal.0c03034](https://doi.org/10.1021/acscatal.0c03034).
- [10] S. Palitsakun, K. Koonkuer, B. Toppr, A. Seubsai, and K. Sudsakom. (2021). "Transesterification of Jatropha oil to biodiesel using SrO catalysts modified with CaO from waste eggshell". *Catal. Commu Catalysis Communications*. **149** : 106233. [10.1016/j.catco.2020.106233](https://doi.org/10.1016/j.catco.2020.106233).
- [11] Z. L. Chung, Y. H. Tan, Y. S. Chan, J. Kannedo, N. M. Muba, M. Ghasemi, M. O. Abdullah. (2019). "Life cycle assessment of waste cooking oil for biodiesel production using waste chicken eggshell derived CaO as catalyst via transesterification". *Biocatalysis and Agricultural Biotechnology*. **21** : 101317. [10.1016/j.bcab.2019.101317](https://doi.org/10.1016/j.bcab.2019.101317).
- [12] Hadrah, M. Kasman, and F. M. Sari. (2018). "Analisis Minyak Jelantah Sebagai Bahan Bakar Biodiesel dengan Proses Transesterifikasi". *Jurnal Daur Lingkungan*. **16** : 10.33087/daurling.v1i1.4.
- [13] Y. S. Kumiawan, K. T. A. Priyanga, P. A. Krisbiantoro, and A. C. Imawan. (2021). "Green Chemistry Influences in Organic Synthesis: a Review". *Journal of*

- Multidisciplinary Applied Natural Science*. **1** (1): 1–12. [10.47352/jmans.v1i1.2](https://doi.org/10.47352/jmans.v1i1.2).
- [14] A. Fadaka, O. Aluko, S. Awawu, and K. Theledi. (2021). “Green Synthesis of Gold Nanoparticles using Pimenta dioica Leaves Aqueous Extract and Their Application as Photocatalyst, Antioxidant, and Antibacterial Agents”. *Journal of Multidisciplinary Applied Natural Science*. **1** (2): 78–88. [10.47352/jmans.v1i2.81](https://doi.org/10.47352/jmans.v1i2.81).
- [15] A. Nurain, P. Sarker, M. S. Rahaman, M. M. Rahman, and M. K. Uddin. (2021). “Utilization of Banana (*Musa sapientum*) Peel for Removal of Pb²⁺ from Aqueous Solution”. *Journal of Multidisciplinary Applied Natural Science*. **1** (2): 117–128. [10.47352/jmans.v1i2.89](https://doi.org/10.47352/jmans.v1i2.89).
- [16] J. Zhang, F. Cui, L. Xu, X. Pan, X. Wang, X. Zhang, T. Cui. (2017). “The development of novel Au/CaO nanoribbons from bifunctional building block for biodiesel production”. *Nanoscale*. **9** (41): 15990–15997. [10.1039/c7nr04890d](https://doi.org/10.1039/c7nr04890d).
- [17] J. Yan, X. Zheng, and S. Li. (2014). “A novel and robust recombinant *Pichia pastoris* yeast whole cell biocatalyst with intracellular overexpression of a *Thermomyces lanuginosus* lipase: Preparation, characterization and application in biodiesel production”. *Bioresource Technology*. **151** : 43–48. [10.1016/j.biortech.2013.10.037](https://doi.org/10.1016/j.biortech.2013.10.037).
- [18] E. Alptekin, M. Canakci, and H. Sanli. (2014). “Biodiesel production from vegetable oil and waste animal fats in a pilot plant”. *Waste Management*. **34** (11): 2146–2154. [10.1016/j.wasman.2014.07.019](https://doi.org/10.1016/j.wasman.2014.07.019).
- [19] Y. Dang, X. Luo, F. Wang, and Y. Li. (2016). “Value-added conversion of waste cooking oil and post-consumer PET bottles into biodiesel and polyurethane foams”. *Waste Management*. **52** : 360–366. [10.1016/j.wasman.2016.03.054](https://doi.org/10.1016/j.wasman.2016.03.054).
- [20] Y. Xiong, W. F. Miao, N. N. Wang, H. M. Chen, X. P. Wang, J. Y. Wang, Q. L. Tan, S. P. Chen. (2019). “Solid alcohol based on waste cooking oil: Synthesis, properties, micromorphology and simultaneous synthesis of biodiesel”. *Waste Management*. **85** : 295–303. [10.1016/j.wasman.2018.12.036](https://doi.org/10.1016/j.wasman.2018.12.036).
- [21] J. M. Marchetti. (2012). “A summary of the available technologies for biodiesel production based on a comparison of different feedstock’s properties”. *Process Safety and Environmental Protection*. **90** (3): 157–163. [10.1016/j.psep.2011.06.010](https://doi.org/10.1016/j.psep.2011.06.010).
- [22] M. Agarwal, G. Chauhan, S. P. Chaurasia, and K. Singh. (2012). “Study of catalytic behavior of KOH as homogeneous and heterogeneous catalyst for biodiesel production”. *Journal of the Taiwan Institute of Chemical Engineers*. **43** (1): 89–94. [10.1016/j.jtice.2011.06.003](https://doi.org/10.1016/j.jtice.2011.06.003).
- [23] S. M. Pavlović, D. M. Marinković, D. Kostić, I. M. Janković-Častvan, L. V. Mojović, M. V. Stanković, V. B. Veljković. (2020). “A CaO/zeolite-based catalyst obtained from waste chicken eggshell and coal fly ash for biodiesel production”. *Fuel*. **267** : 117171. [10.1016/j.fuel.2020.117171](https://doi.org/10.1016/j.fuel.2020.117171).
- [24] A. A. Ayodeji, O. E. Modupe, B. Rasheed, and J. M. Ayodele. (2018). “Data on CaO and eggshell catalysts used for biodiesel production”. *Data in Brief*. **19** : 1466–1473. [10.1016/j.dib.2018.06.028](https://doi.org/10.1016/j.dib.2018.06.028).
- [25] S. Susumu, R. Rusdianasari, and S. Yusi. (2018). “Biodiesel Production from Waste Cooking Oil using Electrostatic Method”. *Indonesian Journal of Fundamental and Applied Chemistry*. **3** (3): 71–76. [10.24845/ijfac.v3.i3.71](https://doi.org/10.24845/ijfac.v3.i3.71).
- [26] A. Santoso, Sumari, U. Urfa Zakiyya, and A. Tiara Nur. (2019). “Methyl Ester Synthesis of Crude Palm Oil Off Grade Using the K₂O/Al₂O₃ Catalyst and Its Potential as Biodiesel” *IOP Conference Series: Materials Science and Engineering*. **515** : 012042. [10.1088/1757-899X/515/1/012042](https://doi.org/10.1088/1757-899X/515/1/012042).
- [27] H. Amrulloh, A. Fatiqin, W. Simanjuntak, H. Afriyani, and A. Annissa. (2021). “Antioxidant and Antibacterial Activities of Magnesium Oxide Nanoparticles Prepared using Aqueous Extract of *Moringa Oleifera* Bark as Green Agents”. *Journal of Multidisciplinary Applied Natural Science*. **1** (1): 44–53. [10.47352/jmans.v1i1.9](https://doi.org/10.47352/jmans.v1i1.9).

utilization of Breed Chicken Eggshells for Biodisel

ORIGINALITY REPORT

28%

SIMILARITY INDEX

5%

INTERNET SOURCES

23%

PUBLICATIONS

16%

STUDENT PAPERS

PRIMARY SOURCES

- | | | |
|---|---|-----|
| <div style="background-color: red; color: white; width: 40px; height: 40px; display: flex; align-items: center; justify-content: center; margin: 0 auto;">1</div> | <p>Submitted to UIN Maulana Malik Ibrahim Malang</p> <p>Student Paper</p> | 1 % |
| <hr/> | | |
| <div style="background-color: magenta; color: white; width: 40px; height: 40px; display: flex; align-items: center; justify-content: center; margin: 0 auto;">2</div> | <p>Daniel de la Flor, Clara López-Aguado, Marta Paniagua, Gabriel Morales, Rafael Mariscal, Juan A. Melero. "Defective UiO-66(Zr) as an efficient catalyst for the synthesis of bio jet-fuel precursors via aldol condensation of furfural and MIBK", Journal of Catalysis, 2021</p> <p>Publication</p> | 1 % |
| <hr/> | | |
| <div style="background-color: purple; color: white; width: 40px; height: 40px; display: flex; align-items: center; justify-content: center; margin: 0 auto;">3</div> | <p>Dimitrij Ješić, Damjan Lašič Jurković, Andrej Pohar, Luka Suhadolnik, Blaž Likozar. "Engineering Photocatalytic and Photoelectrocatalytic CO2 Reduction Reactions: Mechanisms, Intrinsic Kinetics, Mass Transfer Resistances, Reactors and Multi-scale Modelling Simulations", Chemical Engineering Journal, 2020</p> <p>Publication</p> | 1 % |
| <hr/> | | |
| <div style="background-color: teal; color: white; width: 40px; height: 40px; display: flex; align-items: center; justify-content: center; margin: 0 auto;">4</div> | <p>Han Tian, Xiangzhi Cui, Jianlin Shi. "Emerging electrocatalysts for PEMFCs applications:</p> | 1 % |

Tungsten oxide as an example", Chemical Engineering Journal, 2021

Publication

5

Zeynab Amini, Zul Ilham, Hwai Chyuan Ong, Hoorazadeh Mazaheri, Wei-Hsin Chen. "State of the art and prospective of lipase-catalyzed transesterification reaction for biodiesel production", Energy Conversion and Management, 2017

Publication

1 %

6

RA Nurul Moulita, Rusdianasari, Leila Kalsum. "Converting Waste Cooking Oil into Biodiesel using Microwaves and High Voltage Technology", Journal of Physics: Conference Series, 2019

Publication

1 %

7

Aman Santoso, Ida Bagus S. Sumari, Novia Nina Safitri, Anugrah Ricky Wijaya, Daratu Eviana Kusuma Putri. "Activation of Zeolite from Malang as Catalyst for Plastic Waste Conversion to Fuel", Key Engineering Materials, 2020

Publication

1 %

8

Submitted to mvc

Student Paper

1 %

9

Nihan Özveren, M. Özgür Seydibeyoğlu. "The Use of Biodiesel Residues for Heat Insulating

1 %

Biobased Polyurethane Foams", International
Journal of Polymer Science, 2017

Publication

10

Submitted to Chulalongkorn University

Student Paper

1 %

11

juniv.edu

Internet Source

1 %

12

Isaiah Adesola Oke, Lukman Salihu, Idi
Dansuleiman Mohammed, Asani M. Afolabi.
"chapter 91 Overview of Solid Waste
Management of Healthcare and Related
Organisations", IGI Global, 2021

Publication

1 %

13

Rose Fadzilah Abdullah, Umer Rashid, Balkis
Hazmi, Mohd Lokman Ibrahim, Toshiki
Tsubota, Fahad A. Alharthi. "Potential
heterogeneous nano-catalyst via integrating
hydrothermal carbonization for biodiesel
production using waste cooking oil",
Chemosphere, 2021

Publication

1 %

14

Zhijuan Wang, Huajing Zhou, Zilian Liu,
Rongrong Miao, Liang He, Qingqing Guan.
"Walnut-shaped calcium oxide-cancrinite
spheres for transesterification of waste frying
oil", Renewable Energy, 2023

Publication

1 %

15	Submitted to The Technical University of Kenya Student Paper	1 %
----	---	-----

16	Bragadeshwaran Ashok, Kasianantham Nanthagopal, M. Senthil Kumar, Aaditya Ramasamy et al. "An investigation on CI engine characteristics using pork lard methyl ester at various injection pressures and injection timings", International Journal of Green Energy, 2019 Publication	1 %
----	---	-----

17	Maryam Helmi, Kambiz Tahvildari, Alireza Hemmati, Parviz Aberoomand Azar, Aliakbar Safekordi. "Converting waste cooking oil into biodiesel using phosphomolybdic acid/clinoptilolite as an innovative green catalyst via electrolysis procedure; optimization by response surface methodology (RSM)", Fuel Processing Technology, 2022 Publication	1 %
----	---	-----

18	Submitted to Loughborough University Student Paper	1 %
----	---	-----

19	Marlene Lopes, Sílvia M. Miranda, Isabel Belo. "Microbial valorization of waste cooking oils for valuable compounds production – a review", Critical Reviews in Environmental Science and Technology, 2019	1 %
----	--	-----

20

Submitted to University of Liverpool

Student Paper

1 %

21

Elsa Cherian, G. Kalavathy, T. Jayasree Joshi, M. Grace Lydia Phoebe, Baskar Gurunathan. "Importance of nanocatalyst and its role in biofuel production", Elsevier BV, 2022

Publication

1 %

22

Fang-Zheng Su, Yong-Mei Liu, Lu-Cun Wang, Yong Cao, He-Yong He, Kang-Nian Fan. "Ga-Al Mixed-Oxide-Supported Gold Nanoparticles with Enhanced Activity for Aerobic Alcohol Oxidation", Angewandte Chemie International Edition, 2008

Publication

1 %

23

Rasha Khalid Abbas. "Chemical Constituents of the Goat Margarine and Antibacterial Activity against Bacterial Pathogens in Sudan", Journal of Pure and Applied Microbiology, 2019

Publication

1 %

24

Amirul Mukminin, Eka Megawati, Debora Ariyani, I Ketut Warsa, Junety Monde, Sapril Sapril. "Pengaruh Waktu Reaksi Pembuatan Biodiesel dari Minyak Jelantah dengan Bantuan Katalis Basa NaOH terhadap Sifat Fisika dan Kimia Produk Biodiesel", Journal on Education, 2023

1 %

-
- 25 M Al Muttaqii, M Amin, E Prasetyo, R Alviany, L Marlinda. " Production of biodiesel over ZnO-TiO bifunctional oxide catalyst supported on natural zeolite ", IOP Conference Series: Earth and Environmental Science, 2021

Publication

-
- 26 docksci.com 1 %

Internet Source

-
- 27 Submitted to The University of Manchester <1 %

Student Paper

-
- 28 www.pubfacts.com <1 %

Internet Source

-
- 29 Jiadi Liu, Minghuan Liu, Shaoyun Chen, Bingqing Wang, Jin Chen, Da-Peng Yang, Shangzhou Zhang, Wenxiao Du. "Conversion of Au(III)-polluted Waste Eggshell into Functional CaO/Au nanocatalyst for Biodiesel Production", Green Energy & Environment, 2020

Publication

-
- 30 www.matec-conferences.org <1 %

Internet Source

-
- 31 repository.sustech.edu <1 %

Internet Source

32

C. Kayathiri, A.R. Balu, M. Suganya, G. Vinitha, Z. Delci, S. Balamurugan, M. Karthika, S. Anitha, A. Prabavathi. "BaZrO₃ perovskite – A UV light mediated congo red dye deactivator catalyst with good optical switching and antimicrobial abilities green synthesized using Moringa oleifera leaf extract", Materials Science and Engineering: B, 2022

Publication

<1 %

33

Monirul, I. M., H. H. Masjuki, M. A. Kalam, N. W. M. Zulkifli, H. K. Rashedul, M. M. Rashed, H. K. Imdadul, and M. H. Mosarof. "A comprehensive review on biodiesel cold flow properties and oxidation stability along with their improvement processes", RSC Advances, 2015.

Publication

<1 %

34

Rhiannon Moore, Caine Rolleston, Ana Grijalva. "Unlocking the Black Box: To What Extent Are Interactive Classrooms Effective Classrooms in Andhra Pradesh and Telangana, India?", Comparative Education Review, 2021

Publication

<1 %

35

Sri Hidayati, Wisnu Satyajaya, Ahmad Fudholi. "Lignin isolation from black liquor from oil palm empty fruit bunch using acid", Journal of Materials Research and Technology, 2020

<1 %

36

core.ac.uk

Internet Source

<1 %

37

Anita Ramli, Muhammad Farooq, Abdul Naeem, Saleem Khan, Muhammad Hummayun, Azhar Iqbal, Sohail Ahmed, Liaqat Ali Shah. "Chapter 14 Bifunctional Heterogeneous Catalysts for Biodiesel Production using Low Cost Feedstocks: A Future Perspective", IntechOpen, 2017

Publication

<1 %

38

H Heryani, N R Yanti. "Potentials of biomass waste sources for heterogeneous catalyst production", IOP Conference Series: Earth and Environmental Science, 2020

Publication

<1 %

39

Ida Febriana, M Anerasari, KA Ridwan, Taufik Jauhari. "Study of The Effect of Calcium Oxide (CaO) Catalyst Derived From Blood Clam (Anadara Granosa) And Reaction Time To Quality of Biodiesel From Waste Cooking Oil", Journal of Physics: Conference Series, 2020

Publication

<1 %

40

M S Sinaga, Bernandus Petrus, W G T Sitompul. "Production of biodiesel from used cooking oil using blood cockle shell (Anadara Granosa) ash as catalyst", IOP Conference

<1 %

41

text-id.123dok.com

Internet Source

<1 %

42

Hala A. Ibrahim, Hala A. Amin, Samir Bondock. "Effect of antibacterial substance extracted from brown algae on bacteria isolated from wastewater", DESALINATION AND WATER TREATMENT, 2020

Publication

<1 %

43

Mamtaz Dawlatana. "Science and Technology for Sustainable Development", Bangladesh Journal of Scientific and Industrial Research, 2019

Publication

<1 %

44

Piyaphong Yongphet, Junfeng Wang, Tanongkiat Kiatsiriroat, Dongbao Wang et al. "Enhancement of biodiesel production from soybean oil by electric field and its chemical kinetics", Chemical Engineering and Processing - Process Intensification, 2020

Publication

<1 %

45

Zeenat Arif, Naresh K. Sethy, P. K. Mishra, P. Kumar. "Chapter 8 Green Synthesis of Nanomaterials from Biomass Waste for Biodiesel Production", Springer Science and Business Media LLC, 2023

<1 %

46

D. A. Kamel, H. A. Farag, N. K. Amin, Y. O. Fouad. "Biodiesel synthesis from non-edible oils by transesterification using the activated carbon as heterogeneous catalyst", International Journal of Environmental Science and Technology, 2016

<1 %

Publication

Exclude quotes Off

Exclude matches Off

Exclude bibliography Off